

KAOLINITE INTERCALATION PRECURSORS

YANFENG LI, DEWEN SUN, XIAOBING PAN, AND BO ZHANG

State Key Laboratory of Applied Organic Chemistry, College of Chemistry and Chemical Engineering, Institute of Biochemical Engineering & Environmental Technology, Lanzhou University, Lanzhou 730000, China

Abstract—The preparation and characterization of intercalated kaolinite is important for industries such as those using nanocomposites, but the number of compounds that can be intercalated into these clay minerals is rather limited. The purpose of this study was to expand the range of possible intercalants by developing intercalation precursors using both single and multiple (co-intercalation) precursor agents. Characterization of the resulting precursors was by X-ray powder diffraction (XRD), Fourier transform infrared spectroscopy (FTIR), thermogravimetric analysis (TGA), and differential thermal analysis (DTA). The results show that the most successful single intercalation agent was DMSO and, among the co-intercalation agents, the DMSO/CH₃OH system was the best. The preparation and characterization of kao-DMSO-KAc showed that the displacement reaction is the most efficient way to expand the interlayer spacing of kaolinite. At the same time, the lateral-bilayer arrangement of the Ac⁻ in the interlayers was proven by study of de-intercalation of kao-KAc under high temperature.

Key Words—Arrangement, Co-intercalation Agents, De-intercalation, Guest-Displacement Reaction, Intercalation Precursor, Kaolinite, Lateral-bilayer, Single Intercalation System, Thermal Decomposition, X-ray Analyses.

Terminology—DMF: dimethyl formamide; DMSO: dimethyl sulfoxide; HAc: acetic acid; KAc: potassium acetate; NaAc: sodium acetate; NH₄Ac: ammonium acetate.

INTRODUCTION

Intercalation is well known as a means of forming inorganic-organic nanocomposites under mild conditions and clay minerals are common host materials for intercalation chemistry. Kaolinite is one of the most ubiquitous clay minerals on Earth, commonly found in soils, sediments, and sedimentary rocks, and is one of the most important industrial raw materials. Kaolinite has a 1:1-type layered structure with high crystallinity and unique structure: one side of the interlayer space is covered with hydroxyl groups of the Al₂(OH)₄ octahedral sheets and the other side is covered by oxygens of the SiO₄ tetrahedral sheets (Benco *et al.*, 2001). Because of the hydrogen-bonding between its layers, kaolinite has often been classified as non-expandable, while only a limited number of polar organic compounds such as dimethylsulfoxide (DMSO), deuterated dimethylsulfoxide (Martens *et al.*, 2002), formamide (Horváth *et al.*, 2005), N-methylformamide, dimethylformamide, acetamide, potassium acetate (Frost *et al.*, 1999), octadecylamine, and methanol (Cabedo *et al.*, 2004) can be intercalated directly. In recent years, intercalation reactions of kaolinite have been extended by the so-called “guest displacement” method (Komori *et al.*, 1999) where kaolinite intercalation compounds can be replaced by a new guest species.

Millions of tons of kaolinite are used each year in a large variety of applications, such as ceramics, paper coating, paper filling, paint extender, rubber filler, plastic filler, cracking catalysts, and cements (Bundy and Ishley, 1991; Murray *et al.*, 1993; Murray, 2000). Improvement of the properties of kaolinite by the intercalation method is difficult, however, because of the high passivity of the material. Increasing interest in possible new applications of kaolinite as a natural, common, and cheap material justifies a systematic study of the intercalation process.

Six pre-requisites need to be satisfied if guest molecules are to be intercalated successfully into kaolinite: (1) the hydrogen bonds must be broken; (2) the *d* spacing of the clay has to be expanded; (3) the organophilicity of kaolinite has to be modified; (4) the intercalation guest must have strong polarity; (5) the intercalation guest monomer must be of an appropriate size; and (6) the intercalated organic molecule should be bound with some functional group in the clay such as an hydroxyl of Al₂(OH)₄ octahedral sheets, an oxygen atom of a SiO₄ tetrahedron, or both (Zhang *et al.*, 2007).

Intercalation of a large number of solvents has been tested but little information about the effect of synthesis parameters on the intercalation process has been reported. The aim of the present work was to study the synthesis parameters that affect the process of preparing the precursors, using a single intercalation agent and using several co-intercalation agents. With a versatile and effectively benign approach based on displacing the

* E-mail address of corresponding author:
liyf@lzu.edu.cn
DOI: 10.1346/CCMN.2009.0570610

intercalation guest, the kao-KAc (K_2) was prepared by the guest displacement reaction between KAc and DMSO. The synthesis parameters of the intercalation process and the arrangement of the organic molecules (Ac^-) in the interlayer region are also discussed.

EXPERIMENTAL SECTION

Chemicals and instrumentation

The natural clay mineral used in this work was kaolinite supplied by the China-kaolinite Company, Wuhan, with a particle size of 5–10 μm . Hydrochloric acid was supplied by the Beijing-Chemical Plant, Beijing. The DMSO, methanol, ethanol, HAc, KAc, NaAc, NH₄Ac, DMF, and urea used in this study, without further purification, were manufactured by the Fuchen-Chemical reagent Factory, Tianjin, China. All were of analytical reagent grade.

Wide-angle X-ray analyses were carried out using an XRD-6000 equipped with a vertical goniometer and a curved graphite diffracted-beam monochromator. The radiation applied was CuK α ($\lambda = 1.54 \text{ \AA}$) from a long, fine-focus Cu tube, operating at 40 kV and 30 Ma from 2 to $80^\circ 2\theta$. Thermal decomposition of the precursors was carried out using a Perkin-Elmer, TGA-7 type thermogravimetric analyzer at a heating rate of $10^\circ\text{C}/\text{min}$ from room temperature to 800°C under an atmosphere of N₂. The thermal degradation temperature was taken as the minimum of the first derivative of the weight loss with respect to time (this point corresponds to the maximum weight-loss rate). The DTA data were collected using a Dupang-1090 DTA Instrument in an air atmosphere, the

heating rate was $10^\circ\text{C}/\text{min}$, and Al₂O₃ was used as a reference. Fourier-transform infrared spectra of these precursors' surfaces were recorded in the range 4000–350 cm^{-1} in a 670-type infrared Fourier transform spectrometer, using the KBr pellet technique (KBr:sample = 100:1~2).

Preparation of samples

5 g of crude kaolinite was stirred in 60 mL of 5.0 mol/L hydrochloric acid at 80°C . After stirring for 8 h, the mixture was filtered and washed five times with distilled water until the pH value of the mother liquor was 7, in order to ensure removal of any unwanted cations such as Ca²⁺, Fe³⁺, etc. The purified kaolinite (K_0) was dried at 100°C under vacuum for 5 h (Cabedo *et al.*, 2004).

To prepare kaolinite precursors with a single intercalation agent (DMSO, KAc, NaAc, NH₄Ac, Urea, DMF), 5 g of purified kaolinite was stirred with 100.0 mL of organic liquid or solution under different conditions (see below). The intercalation mixture was filtered and washed three times with hot (~50°C) ethanol or water in order to remove excess organic compound (Belver *et al.*, 2002; Olejnik *et al.*, 1970; Elbokl and Detellier, 2006).

To prepare the kaolinite precursor with co-intercalation agents, five organic agents were chosen as possible guest intercalates: DMSO/HAc, DMSO/CH₃OH, DMSO/H₂O, DMSO/NaAc, and DMSO/KAc. 5 g of purified kaolinite was stirred with 100.0 mL of DMSO and 10 mL of organic compound (HAc, CH₃OH, H₂O) or 10 mL of aqueous solution of the organic agent (NaAc,

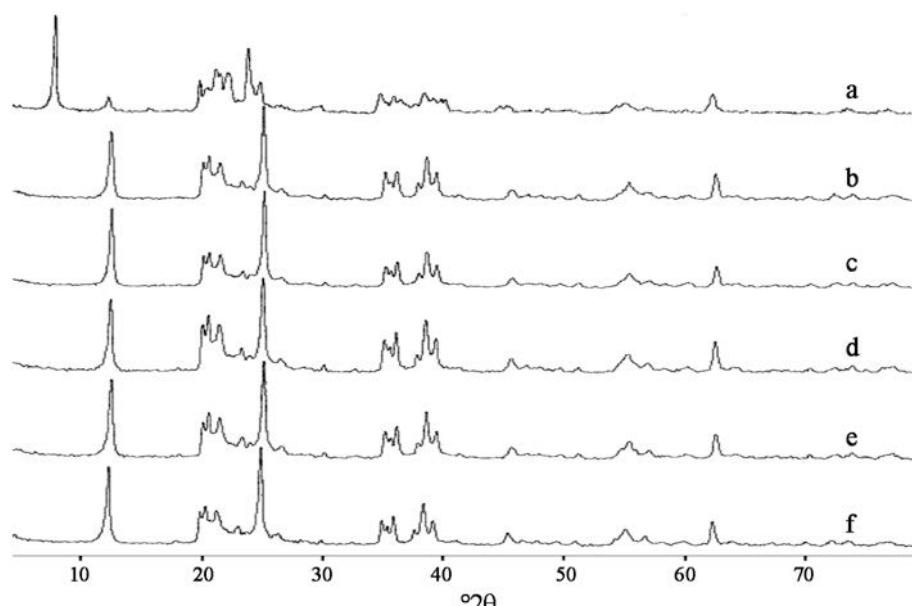


Figure 1. WXRD of kaolinite precursors with single intercalation agents: (a) Kao-DMSO; (b) Kao-KAc; (c) Kao-NaAc; (d) Kao-NH₄Ac; (e) Kao-Urea; and (f) Kao-DMF.

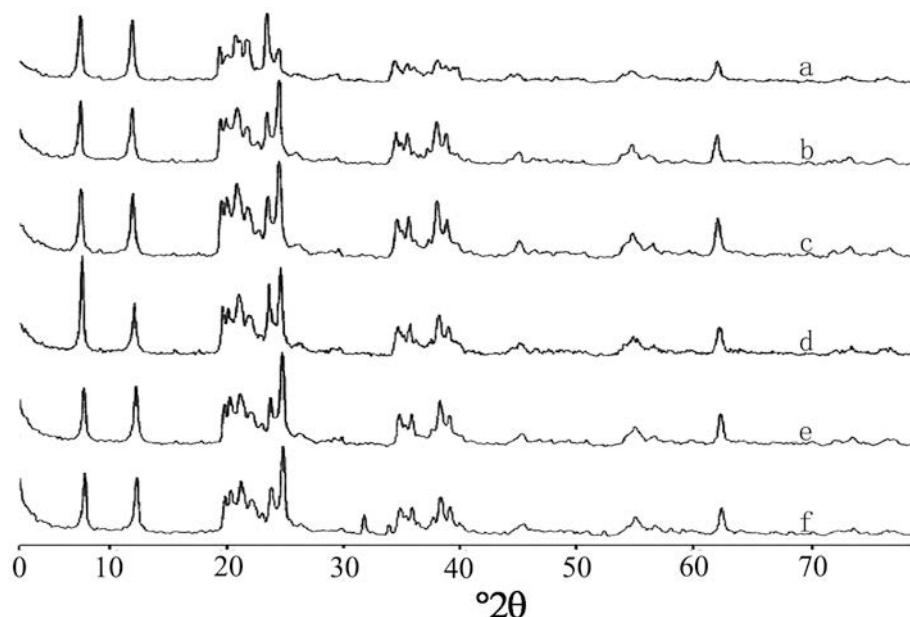


Figure 2. WXRD of kaolinite precursors with co-intercalation agents: (a) DMSO; (b) DMSO-HAc; DMSO/NaAc; (d) DMSO/H₂O; (e) DMSO/KAc; and (f) DMSO/CH₃OH.

KAc) at the concentration of 20 wt.% under different conditions (see below). The intercalation system was then filtered and washed three times with ethanol.

The kao-KAc precursor was prepared by the guest-displacement reaction between KAc and DMSO. The aqueous solution of KAc was stirred in with kao-DMSO/CH₃OH (K₁), and then the system was filtered and washed with hot (65°C) water.

RESULTS AND DISCUSSION

Wide X-ray diffraction

The primary hydrogen bonds between the clays can be broken by a strong polar organic molecule (DMSO, $\mu = 3.9$ D), and the new hydrogen bonds between the strong polar molecule and the tetrahedral or the octahedral sheet can be formed easily. The wide X-ray diffraction (WXRD) of kao-DMSO (Figure 1a) shows that the d_{001} spacing of kao-DMSO was 1.118 nm compared to 0.72 nm of the raw kaolinite, the difference being due to the intercalation of DMSO in the kaolinite. The rate of intercalation was 87.72%. The intercalation

rates (IR), given as percentages, were calculated as described by equation 1.

$$IR = (I_{i(001)} / (I_{k(001)} + I_{i(001)})) \times 100\% \quad (1)$$

where $I_{i(001)}$ is the peak intensity observed for the intercalate and $I_{k(001)}$ is the peak intensity observed for kaolinite. The basal spacing of the other precursors increased only slightly, according to the WXRD curves (Figure 1) of the precursors with a single intercalation agent. Their intercalation rates were negligible.

The lattice structure (Figure 2) and the reaction conditions and intercalation rates for different precursors with the co-intercalation agents (Table 1) show that the d_{001} spacing of kao-DMSO/CH₃OH is largest while the intercalated ratio of kao-DMSO/H₂O is the largest of these precursors. The d_{001} spacing of the precursor is fundamental to the intercalation of organic molecules in the future, and the intercalated ratio can be improved by temperature or reaction-time adjustment. The DMSO/CH₃OH agents were, therefore, chosen for this study.

The relationship between the ratio DMSO/CH₃OH and the amount of organic matter fixed in the solids and

Table 1. Summary of reaction conditions and intercalated ratio for different precursors with the co-intercalation agents.

Phase	Solvent	T (°C)	t (h)	d_{001} (nm)	IR (%)
Kao-DMSO	–	90	48	1.118	51.90
Kao-DMSO/HAc	HAc	90	48	1.128	51.35
Kao-DMSO/NaAc	NaAc	90	48	1.123	51.02
Kao-DMSO/H ₂ O	H ₂ O	90	48	1.126	65.79
Kao-DMSO/KAc	KAc	90	48	1.125	49.22
Kao-DMSO/CH ₃ OH	CH ₃ OH	90	48	1.130	51.45

Table 2. Summary of reaction conditions and intercalated ratio for the precursors with the DMSO/CH₃OH agents.

Sample	CH ₃ OH% (V%)	T (°C)	t (h)	d ₀₀₁ (nm)	IR (%)
Kao-DMSO/ CH ₃ OH effect by concentration	0	80	48	1.118	51.38
	10	80	48	1.129	51.47
	20	80	48	1.128	54.00
	30	80	48	1.127	40.18
	40	80	48	1.127	30.65
	50	80	48	0.720	0
	70	80	48	0.720	0
Kao-DMSO/ CH ₃ OH effect by temperature	15	40	48	1.130	30.53
	15	60	48	1.125	43.94
	15	80	48	1.126	54.14
	15	90	48	1.126	53.38
	15	100	48	1.125	23.60
	15	120	48	1.127	7.50
Kao-DMSO/ CH ₃ OH effect by time	15	85	24	1.129	25.72
	15	85	48	1.127	53.97
	15	85	72	1.127	70.81
	15	85	96	1.126	88.50
	15	85	120	1.125	91.09
	15	85	144	1.128	90.73
	15	85	168	1.129	90.55

the basal spacing of the intercalated solids is significant. Seven samples were prepared at 80°C for 48 h, with different DMSO/CH₃OH ratios. The basal spacings and the intercalated ratios of the precursors (tabulated in Table 2) revealed that the d₀₀₁ spacing of the precursors prepared with co-intercalation agents of DMSO/CH₃OH is ~1.128 nm, while the basal spacing is 1.118 nm for a

single system of DMSO. In the first case, the organic molecule (DMSO) and the solvent (CH₃OH) are actually intercalated together, while in the second case, only the fixation of DMSO occurs. The intercalated ratio first increased then decreased with increasing CH₃OH. The intercalation process stops when the amount of CH₃OH exceeds 50% (v/v). The results indicate that methanol

Table 3. Summary of reaction conditions and intercalated ratio for K₁-KAc.

Sample	C _{KAc} (mol/L)	T (°C)	t (h)	d ₀₀₁ (nm)	IR (%)
K ₁ -KAc effect by concentration	2	30	72	1.414	75.76
	4	30	72	1.421	89.29
	6	30	72	1.413	88.50
	8	30	72	1.412	89.29
	10	30	72	1.423	89.29
	12	30	72	1.419	89.29
	8	0	24	1.414	91.74
K ₁ -KAc effect by temperature	8	20	24	1.411	91.74
	8	40	24	1.412	95.24
	8	60	24	1.408	95.24
	8	80	24	1.410	90.91
	8	90	24	1.424	89.29
K ₁ -KAc effect by time	5	50	2	1.423	94.34
	5	50	4	1.419	91.74
	5	50	6	1.396	90.09
	5	50	8	1.416	91.74
	5	50	12	1.430	94.34
	5	50	16	1.411	90.91
	5	50	20	1.415	91.74

has an important role in the intercalation process of the co-intercalation agents. The strong polar organic molecules may be clustered to form aggregates through hydrogen bonds. Pure DMSO liquid is very viscous ($\eta = 2.24 \text{ mPa}\cdot\text{s}$ at 20°C). The large aggregates and the great viscosity had a negative effect on the formation of the precursor. The aggregates and viscosity of DMSO were reduced by adding methanol ($\eta = 0.6 \text{ mPa}\cdot\text{s}$ at 20°C). When the CH_3OH content was >50%, methanol intercalated

into the clays first because too few sites were available for DMSO molecules and, consequently, the amount of DMSO fixed was insufficient to swell the clay efficiently. Intercalation is regarded as an equilibrium process between the cleavage of old hydrogen bonds and the formation of new hydrogen bonds. The process of forming hydrogen bonds is exothermic; high temperature restrains the process, as reflected in the intercalation rates of the kao-DMSO/ CH_3OH , which is

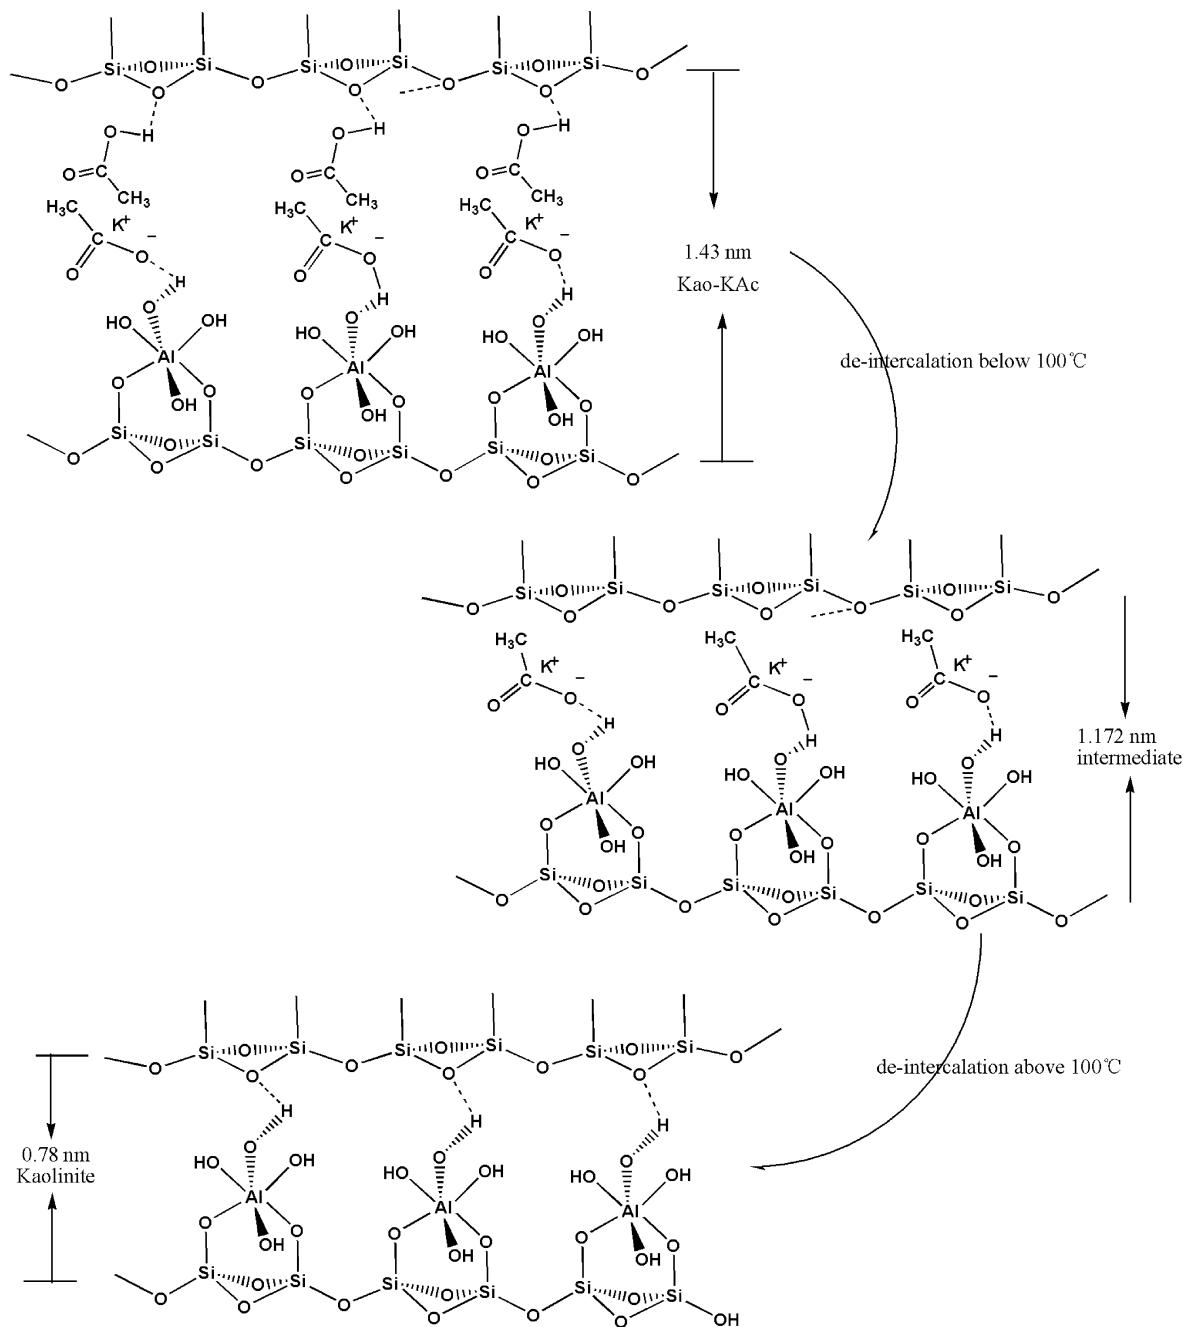


Figure 3. Illustration of the de-intercalated process of K_2 .

close to 54.14% at 80°C and only 7.5% at 120°C. The time allowed for intercalation plays an important role in this process, the intercalation rates increase almost linearly with respect to reaction time and then level off above 120 h.

The reactivity of DMSO/CH₃OH-treated kaolinite toward KAc was also investigated. The KAc molecules penetrate rapidly and easily even under ambient conditions (low concentration, room temperature, and short time), and the ratio of intercalated precursors prepared with KAc under different reaction conditions is high (Table 3). Intercalation of DMSO weakens the cohesion energies of the kaolinite stacking, and incorporation of DMSO transforms the surfaces of the clays from natural organophobic to organophilic. Comparing the synthesis conditions for kao-KAc and kao-DMSO/CH₃OH-KAc samples, pre-intercalation with the DMSO/CH₃OH agents followed by a displacement reaction between KAc and DMSO is much more effective than a single agent for intercalating the clay.

The *d* spacing of K₂ in this study was 1.43 nm, while a spacing of 1.16 nm was reported by Ledoux and White (1996). The observed 1.43 nm *d* spacing corresponds to a 0.71 nm expansion compared to the original kaolinite. The one CH₃COO⁻ group is 0.406 nm long, so even if the KAc is vertical to the siloxane surface, it falls 0.304 nm short of accounting for the observed expansion of the layers. The arrangement of the Ac⁻ in the interlayers is, therefore, considered to be lateral-bilayer (model shown in Figure 3), and this hypothesis is proved by WXRD of the de-intercalated samples (Figure 4) prepared at different temperatures. The de-intercalated K₂ was investigated because the intercalation is a dynamic equilibrium; the intercalated guest could be de-intercalated under certain conditions. The bonds in the lateral-bilayer are weak and can be destroyed by high temperature. The process of de-intercalation and the XRD spectrum of the de-intercalated samples (Figures 3 and 4, respectively) disclosed that new *d*₀₀₁ peaks = 1.172 nm and 0.78 nm appeared when K₂ was treated at temperatures below 100°C, and the *d*₀₀₁ peak = 1.172 nm disappeared above 250°C. The *d*₀₀₁ peak = 1.172 nm, therefore, could be an indication of the transition state of a K₂ de-intercalated compound when it was treated at high temperature. The loss of one of the HAc molecular layers in the lateral-bilayer caused the decrease in the *d* spacing of ~0.258 nm, and the loss of the other layer caused a decrease of 0.392 nm (approximate length of the CH₃COO⁻ group).

According to these observations, optimal results are obtained when: K₁ is prepared at 85°C for 120 h with the methanol concentration in the range ~10–15%; K₂ is prepared at 50°C for 10 h with the KAc concentration at 5 mol/L.

When the precursors of K₁ and K₂ were prepared under optimal conditions, the lattice structure (Figure 5) of K₀ (a), K₁ (b), and K₂ (c) revealed that up to 93.6% of

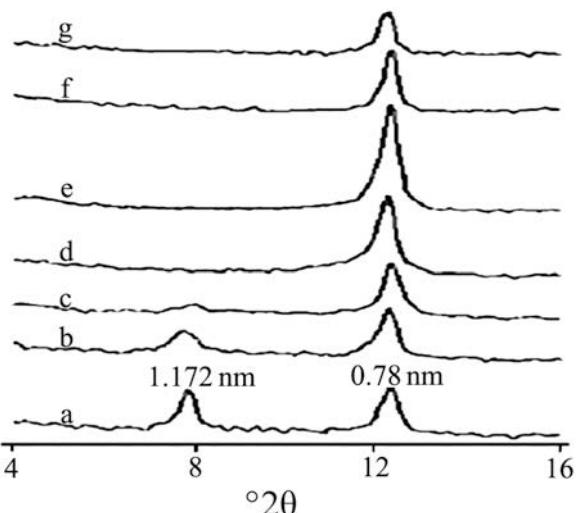


Figure 4. WXRD of the de-intercalated samples: (a) 100°C; (b) 150°C; (c) 200°C; (d) 250°C; (e) 400°C; (f) 400°C; and (g) 500°C.

K₁ and 94.1% of K₂ of the kaolinite were intercalated. The basal spacing *d*₀₀₁ of K₁ expands from 0.72 to 1.13 nm, an increase of 0.41 nm. After treatment of the K₁ intercalation compound with KAc in water, the basal spacing expanded to 1.43 nm from that of K₁ (1.13 nm).

FT-IR spectra

Kaolinite is characterized by a signature O–H stretching pattern consisting of four bands at 3696, 3669, 3654, and 3621 cm⁻¹ (Figure 6a). The attribution of these bands has been the subject of extensive study (Ledoux and White, 1996; Johnston and Stone, 1990; Van der Marel and Beutelspacher, 1976). The band at 3621 cm⁻¹ has been assigned unambiguously to the stretching frequency of the internal hydroxyl group of kaolinite which is believed to be oriented almost parallel to the direction of the (001) layers, pointing in the direction of the octahedral vacancy. The inner-surface

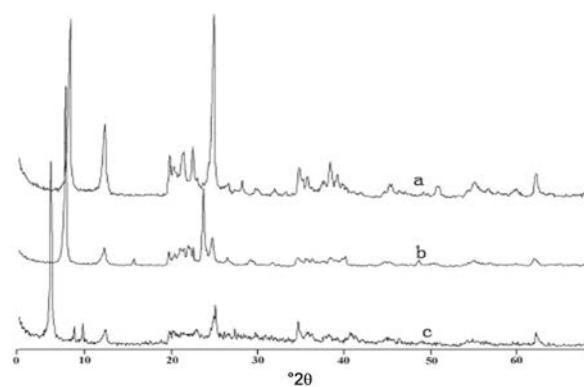


Figure 5. WXRD of raw kaolinite (a), Kao-DMSO/CH₃OH (b), and Kao-KAc (c).

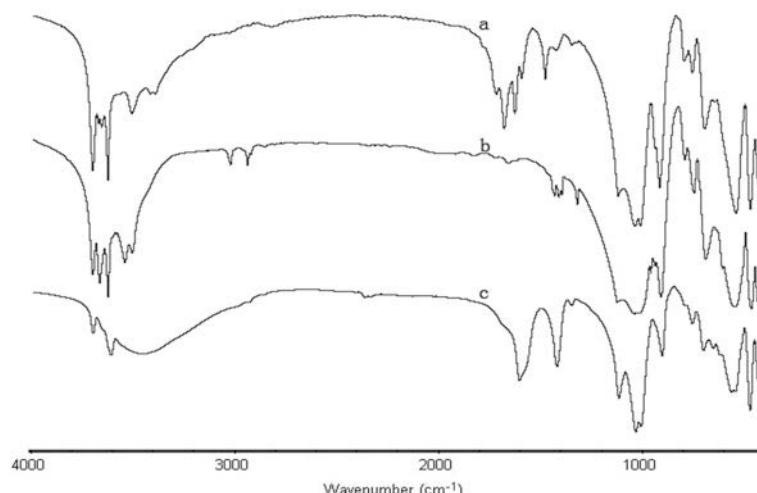


Figure 6. FTIR spectrum of raw kaolinite (a), Kao-DMSO/CH₃OH (b), and Kao-KAc (c).

hydroxyl groups associated with the remaining bands (3696, 3669, and 3654 cm⁻¹) are believed to make an angle of 60–73° with the (001) plane. The inner hydroxyl stretching band at 3621 cm⁻¹ is not usually influenced very much by interlamellar modification reactions since it is separated from the interlamellar surface. In contrast, the three inner-surface hydroxyl stretching bands are very much influenced by interlamellar modifications, as was readily observed for K₁ (Figure 6b). The hydroxyl stretching bands at 3669 and 3653 cm⁻¹ disappeared and new bands at 3663 and 3539 cm⁻¹ appeared, which were assigned to hydrogen-bonding between DMSO and kaolinite. New peaks at 3022 and 2934 cm⁻¹ could be assigned to C–H of DMSO. K₁ also showed deformation bands at 1431 and 1407 cm⁻¹. The results were consistent with previous reports and confirmed that intercalation between kaolinite and DMSO had taken place (Li *et al.*, 2003; Olejnik *et al.*, 1968). The IR spectra of K₂ (Figure 6c), which showed that the peak at 3539 cm⁻¹ was assigned to hydrogen-bonding between DMSO and kaolinite, disappeared and new peaks at 3698 and 3610 cm⁻¹ appeared, which were assigned to hydrogen-bonding between KAc and kaolinite. A further new peak at 1606 and 1418 cm⁻¹ can be assigned to C=O of KAc. These results imply that KAc displaced DMSO and formed a kao-KAc intermediate, which was further supported by WXRD.

Thermogravimetric analyses

Thermogravimetric analyses of the raw kaolinite showed the loss of the water molecules in two steps, the first between room temperature and ~300°C, and the second as a significant weight loss, beginning at 460°C (Figure 7a). At the same time, in the high-temperature region, the differential thermal analyses (Figure 8a) showed three endothermal effects centered at 45, 220, and 510°C, assigned to the removal of the water

adsorbed on the surface of the kaolinite particles and the loss of the structural water of the kaolinite. As for K₀, in the low-temperature region, the DTA of K₁ showed three endothermal effects centered at 40, 180, and 510°C (Figure 8b), assigned to the removal of the volatiles (water and methanol) adsorbed on the surface of the kaolinite particles and to the loss of the structural water of the kaolinite. In the DTA trace of K₂, an endothermic event with a broad peak at 80°C and a very strong exothermic peak at 380°C are noted (Figure 8c). The broad peak at 80°C assigned to the removal of the water adsorbed on the surface of the kaolinite particles and to the strong exothermic peak at 380°C were probably due to the pyrolytic decomposition of the organic component (Ac⁻), overlapping the weight-loss trace of K₂ (Figure 7c). The absence of the broad peak at 510°C in the case of K₂ (Figure 8c) was possibly due to a phase change at 380°C, which was caused by the extended interlayer spacing because of the intercalated KAc.

CONCLUSIONS

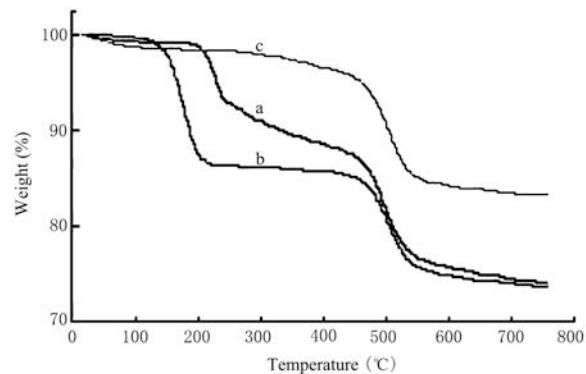


Figure 7. TGA trace of raw kaolinite (a), Kao-DMSO/CH₃OH (b), and Kao-KAc (c).

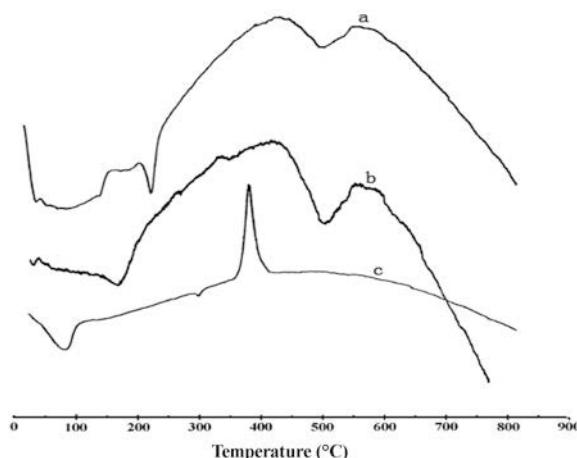


Figure 8. DTA curves of raw kaolinite (a), Kao-DMSO/CH₃OH (b), and Kao-KAc (c).

Kaolinite intercalation precursors have been prepared with a single intercalation agent and with co-intercalation agents by varying the temperature, concentration, and intercalation time used in the reaction process. The co-intercalation agents influence the process, especially in the DMSO/CH₃OH system; a certain amount of CH₃OH is necessary to accelerate the intercalation reaction. K₂ was prepared by a displacement reaction between KAc and DMSO, and the guest displacement reaction is an effective means of achieving the intercalation process. The lateral-bilayer arrangement of the organic molecules (Ac⁻) in the interlayer region was also highlighted.

ACKNOWLEDGMENTS

The authors are grateful for financial support from the key research project of Gansu Province, China (2GS064-A52-036-02).

REFERENCES

- Barrios, J., Plançon, A., Cruz, M.I., and Tchoubar, C. (1977) Qualitative and quantitative study of the stacking faults in a hydrazine-treated kaolinite-relationship with the infrared spectra. *Clays and Clay Minerals*, **25**, 422–429.
- Belver, C., Muñoz, M.A., and Vincente, M.A. (2002) Chemical activation of a kaolinite under acid and alkaline conditions. *Chemistry of Materials*, **14**, 2033–2043.
- Benco, L., Tunega, D., Hafner, J., and Lischka, H. (2001) Upper limit of the O—H···O hydrogen bond: Ab initio study of the kaolinite structure. *Journal of Physical Chemistry B*, **105**, 10812–10817.
- Bundy, W.M. and Ishley, J.N. (1991) Kaolin in paper filling and coating. *Applied Clay Science*, **5**, 397–420.
- Cabedo, L., Gimeneza, E., Lagaronb, J.M., Gavarab, R., and Saura, J.J. (2004) Development of EVOH-kaolinite nanocomposites. *Polymer*, **45**, 5233–5238.
- Elbokl, T.A. and Detellier, C. (2006) Aluminosilicate nanohybrid materials: Intercalation of polystyrene in kaolinite. *Journal of Physical and Chemistry of Solids*, **67**, 950–955.
- Frost, R.L., Kristof, J., Horvath, E., and Kloprogge, J.T. (1999) Modification of kaolinite surfaces through intercalation with potassium acetate, II. *Journal of Colloid and Interface Science*, **214**, 109–117.
- Horváth, E., Kristóf, J., Frost, R.L., Jakab, E., Makó, E., and Vágvölgyi, V. (2005) Identification of superactive centers in thermally treated formamide-intercalated kaolinite. *Journal of Colloid and Interface Science*, **289**, 132–138.
- Johnston, C.T. and Stone, D.A. (1990) Influence of hydrazine on the vibrational modes of kaolinite. *Clays and Clay Minerals*, **38**, 121–128.
- Komori, Y., Sugahara, Y., and Kuroda, K. (1999) Direct intercalation of poly(vinylpyrrolidone) into kaolinite by a refined guest displacement method. *Chemistry of Materials*, **11**, 3–6.
- Ledoux, R.L. and White, J.L.J. (1996) Infrared studies of hydrogen bonding interaction between kaolinite surfaces and intercalated potassium acetate, hydrazine, formamide, and urea. *Journal of Colloid and Interface Science*, **21**, 127–152.
- Li, B.G., Hu, Y., Zhang, R., Chen, Z.Y., and Fan, W.C. (2003) Preparation of the poly(vinyl alcohol)/layered double hydroxide nanocomposite. *Materials Research Bulletin*, **38**, 1567–1572.
- Martens, W.N., Frost, R.L., Kristof, J., and Horvath, E. (2002) Modification of kaolinite surfaces through intercalation with deuterated dimethylsulfoxide. *Journal of Physical Chemistry B*, **106**, 4162–4171.
- Murray, H.H. (2000) Traditional and new applications for kaolin, smectite, and palygorskite: a general overview. *Applied Clay Science*, **17**, 207–221.
- Murray, H.H., Bundy, W., and Harvey, C. (1993) *Kaolin Genesis and Utilization*. Special Publication No. 1, The Clay Minerals Society, Boulder, CO, USA, 43 pp.
- Olejnik, S., Aylmore, L.A.G., Posner, A.M., and Quirk, J.P. (1968) Infrared spectra of kaolin mineral-dimethyl sulfoxide complexes. *Journal of Physical Chemistry*, **72**, 241–249.
- Olejnik, S., Posner, A.M., and Quirk, J.P. (1970) The intercalation of polar organic compounds into kaolinite. *Clay Minerals*, **8**, 421–434.
- Van der Marel, H.W., and Beutelspacher, H. (1976) *Atlas of Infrared Spectroscopy of Clay Minerals and their Admixtures*. Elsevier, Amsterdam.
- Zhang, B., Li, Y.F., Pan, X.B., Jia, X., and Wang, X.L. (2007) Intercalation of acrylic acid and sodium acrylate into kaolinite and their in situ polymerization. *Journal of Physics and Chemistry of Solids*, **68**, 135–142.

(Received 20 March 2009; revised 30 July 2009; Ms. 296; A.E. R.J. Pruett)