

# Lead-free piezoceramics: Status and perspectives

Jürgen Rödel and Jing-Feng Li, Guest Editors

The field of lead-free piezoceramics, which aims to replace lead zirconate titanate (PZT) and related perovskite materials, has been vibrant for almost 15 years. Once the science in this field attained a certain stage of maturity, materials with properties better than PZT have appeared, and the first products are about to reach the marketplace. This article describes the three most promising lead-free piezoceramics currently under discussion to replace PZT. Each has a pronounced property profile geared for specific applications. Guidelines for directions for fundamental future research on as well as technology transfer to industry of lead-free piezoceramics are provided.

## Introduction

European Union (EU) legislation on the restriction of hazardous substances<sup>1</sup> as well as an article<sup>2</sup> in *Nature* about 15 years ago provided the triggers for a strong effort into the science and technology of lead-free piezoceramics, with many stakeholders coming into play. While EU legislation restricts the use of lead in piezoelectric devices unless exempted under specific conditions,<sup>1</sup> the article in *Nature* suggests that lead-free compositions may now be available to replace lead in certain piezoceramic applications.<sup>2</sup> With the goal to reduce the production and waste disposal of toxic lead, research on lead-free piezoceramics strives to make lead zirconate titanate (PZT) and similar perovskite materials redundant. ShROUT and Zhang<sup>3</sup> have summarized the complexity of this task in a concise manner.


The scope of this endeavor to develop lead-free piezoceramics can be gleaned by considering the history of PZT,<sup>4,5</sup> which highlights many years of development. The toxicity of lead, including risks to the environment during mining, processing, and disposal, is the driving force for this research. The article by Bell and Deubzer<sup>6</sup> in this issue summarizes the current level of understanding. Legislation in Europe, and in many other parts of the world,<sup>7</sup> to restrict and reduce hazardous substances such as lead has proven to be a strong driving force toward research into nontoxic replacements. Review processes and interactions with industry to address a variety

of legislative directives have been developed for different applications. Exemption 7(c)-I, for example, has been recently reviewed and provides an exemption for lead in piezoelectronic devices until July 2021, with applications for further extension of this exemption due to the European commission by January 2020. Bell and Deubzer<sup>6</sup> have outlined current legislation and future options.

Piezoelectricity describes the creation of an electric charge in response to a mechanical stress. The converse effect is the development of a strain as a function of an applied electric field (**Figure 1**). The proportionality constant is identical for both cases and is described as the piezoelectric coefficient,  $d$ .<sup>4,8</sup> Since polarization is a vector and stress a second rank tensor, the piezoelectric constant must be written as a third rank tensor, but can be transformed to a second rank matrix.<sup>9</sup> As we are considering the replacement of PZT and of related materials, which are ferroelectrics and are converted to piezoelectrics by a poling process, ferroelectric crystal structures are becoming important.


Domains in ferroelectrics (**Figure 2**) can be considered to be a form of twins that develop at the paraelectric/ferroelectric phase transition in order to reduce the elastic and electrostatic energies.<sup>10</sup> Application of an electric field may lead to lattice extension (intrinsic contribution to the piezoelectric effect), domain-wall movement resulting in a strain contribution (extrinsic contribution to the piezoelectric effect),

Jürgen Rödel, TU Darmstadt, Germany; Tsinghua University, China; and Tokyo Institute of Technology, Japan; roedel@ceramics.tu-darmstadt.de  
Jing-Feng Li, Tsinghua University, China; jingfeng@tsinghua.edu.cn  
doi:10.1557/mrs.2018.181

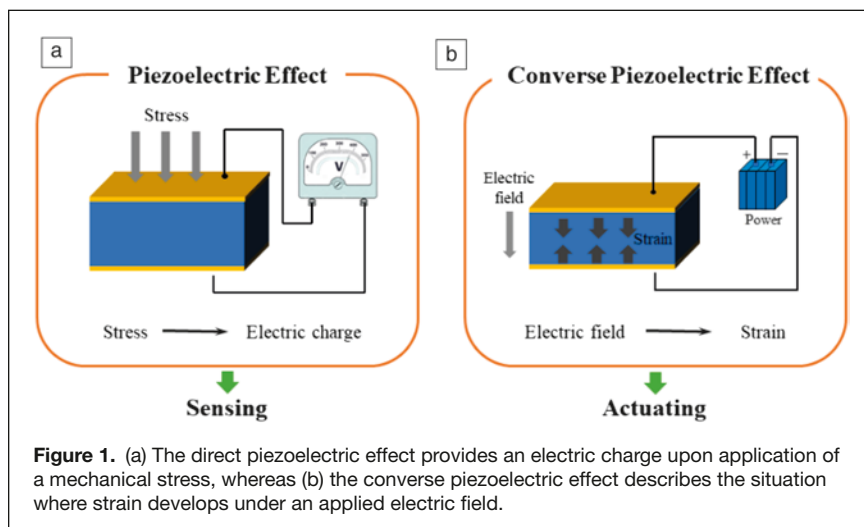

and phase transitions.<sup>11</sup> Consequently, the thermodynamics of the different crystal symmetries (**Figure 3**) is of paramount importance for understanding and designing piezoelectric materials. In particular, the anisotropic flattening of the free energy along nonpolar directions is key for good piezoelectric properties, as it facilitates easy rotation of the polarization vector.<sup>11,12</sup> This important topic, contrasting piezoelectric mechanisms between PZT-related materials and new lead-free compositions, is covered in the article by Damjanovic and Rossetti in this issue.<sup>13</sup>

Note that domain wall movement, as well as phase transformations, are strongly hysteretic processes, which may lead to energy dissipation in the material. A temperature increase may then prompt thermal runaway and limit material performance. Hence, an important distinction in piezoceramics is between soft (high strain, high losses) and hard (low strain, low losses) piezoceramics.<sup>14</sup> A further classification stems from the pertinent applied field. Piezoelectric properties under

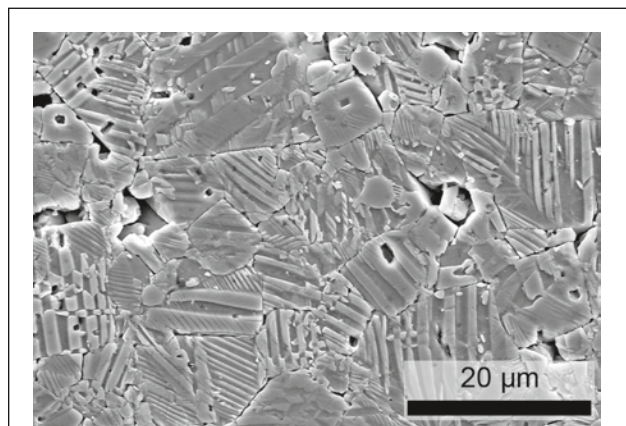

**Figure 2.** Scanning electron microscope micrograph of an etched surface of  $(\text{K}, \text{Na})_{0.94}\text{Li}_{0.6}\text{NbO}_3$  that features a complex domain structure in the polycrystalline grain ensemble. Courtesy: J.L. Zhang, Shandong University.


low driving field (small signal properties) and under high driving field (large signal properties) are relevant for different applications.

### Lead-free material options

The endeavor to find new lead-free perovskites has mostly focused on mimicking PZT. In PZT, a so-called morphotropic phase boundary (MPB) forms and provides properties mostly independent of temperature. This MPB features changes in phase structure with just composition and not temperature. Elements with high ionic polarizability, low cost,<sup>7</sup> and low environmental impact<sup>15</sup> are required. Due to the similar electronic structure of bismuth and lead with the lone  $2s$ -electron pair facilitating hybridization with oxygen, sodium-bismuth-titanate-based (NBT) materials have been contemplated since 1991.<sup>16</sup> These materials are typically relaxors and offer complex phase diagrams.<sup>17</sup> Consequently, dedicated studies of *in situ* phase transitions using scattering techniques such as neutron and synchrotron diffraction played an important role in elaborating structure–property relationships.<sup>17,18</sup> The current understanding of lead-free relaxor-based piezoceramics is discussed in the article by Paterson et al. in this issue.<sup>19</sup>

“Lead-free at last” was the title chosen by Cross<sup>20</sup> to accompany a paper by Saito et al.<sup>2</sup> on the development of potassium sodium niobate (KNN)-based lead-free piezoceramics. These materials feature optimum properties at a polymorphic phase transition with attendant drawbacks of strong temperature dependence.<sup>21,22</sup> More recent research has focused on chemical modifications to provide enhanced temperature stability of the piezoelectric properties.<sup>23</sup> This approach and attendant materials are discussed by Wang et al.<sup>24</sup> in their article in this issue.

Liu and Ren<sup>25</sup> proposed an alternative developmental path to mimicking PZT in 2009, using barium titanate as the base material, doping it with calcium and zirconium, and thus furnishing it with a tricritical point<sup>25</sup> or convergence region where the cubic, orthorhombic, tetragonal, and rhombohedral phases coexist.<sup>26</sup> This material again features a complex phase structure with good properties, albeit limited by a low Curie temperature. In their article in this issue, Gao et al.<sup>27</sup> discuss structure–property relationships for different compositions in the pseudobinary phase diagram  $\text{Ba}(\text{Zr}, \text{Ti})\text{O}_3 \cdot (\text{Ba}, \text{Ca})\text{TiO}_3$ . A new material class based on bismuth ferrite (BF) addresses the needs for high-temperature applications. While the first publications on bismuth ferrite-barium titanate (BF-BT) are already several years old,<sup>28</sup> there has been recent progress by a number of researchers. Most appealing is the promise for use of BF-BT at high temperatures, not only replacing PZT, but also considerably improving high-temperature capabilities.<sup>29</sup> In a study by Lee et al.,<sup>29</sup> excellent piezoelectric properties with a Curie temperature in excess of  $400^\circ\text{C}$  were reported when BF-BT with the addition of either  $\text{Bi}_{1.05}\text{GaO}_3$  or

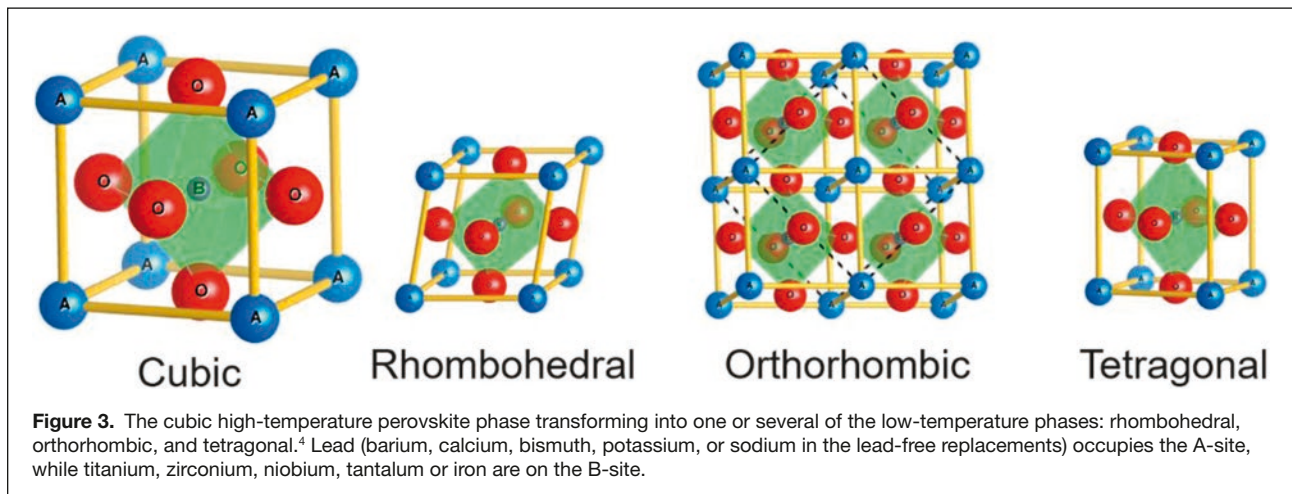


$\text{Bi}_{1.05}(\text{Zn}_{0.5}\text{Ti}_{0.5})\text{O}_3$  was sintered and then quenched. Recently, a correlation of the phase diagram of BF-BT with electrical properties was achieved.<sup>30</sup> Similarly, it was demonstrated that an air quenching treatment in BF-BT affords an improvement in piezoelectric properties through salient changes in atomic structure.<sup>31</sup>


**Figure 4** summarizes the evolution in output of publications and patents in the field of lead-free piezoceramics. Work by many researchers has led to a secondary effect (i.e., development of spin-off nonpiezoelectric applications). The new insight, notably of bismuth-based perovskites, has spawned new research fields into oxygen conductors,<sup>33</sup> high-temperature dielectrics,<sup>34</sup> and energy-storage materials.<sup>35</sup> Similarly, a greater understanding of niobate-based materials has yielded the development of new antiferroelectric niobates for energy storage<sup>36</sup> and for electrocalorics.<sup>37</sup>

**Future directions**

While legislation in Europe and other regions has provided a strong impetus for further research, intense subsequent efforts have brought our scientific understanding close to the level of knowledge on lead-containing piezoceramics. This is particularly true for structural investigations of lead-free piezoceramics, where complementary *in situ* (temperature-, stress- and electric-field-dependent) neutron and synchrotron scattering techniques have provided a highly advanced understanding.<sup>38</sup> As a result, avenues have opened up for new materials with properties better than PZT for select applications.<sup>39</sup> For example, NBT-based materials have advantages over PZT in high-power applications,<sup>40</sup> and KNN can be sintered with nickel for multilayer applications, with nickel providing high electromigration resistance and stability when subjected to high applied electric fields.<sup>41</sup> In the area of thin films, KNN materials offer excellent properties.<sup>42</sup> Additionally, KNN-based ceramics are preferentially used for medical imaging transducers of 1–3 structured composites (fibrous inclusions in continuous matrix).<sup>43,44</sup> Our current knowledge of some of the primary piezoelectric properties (e.g., temperature-dependent

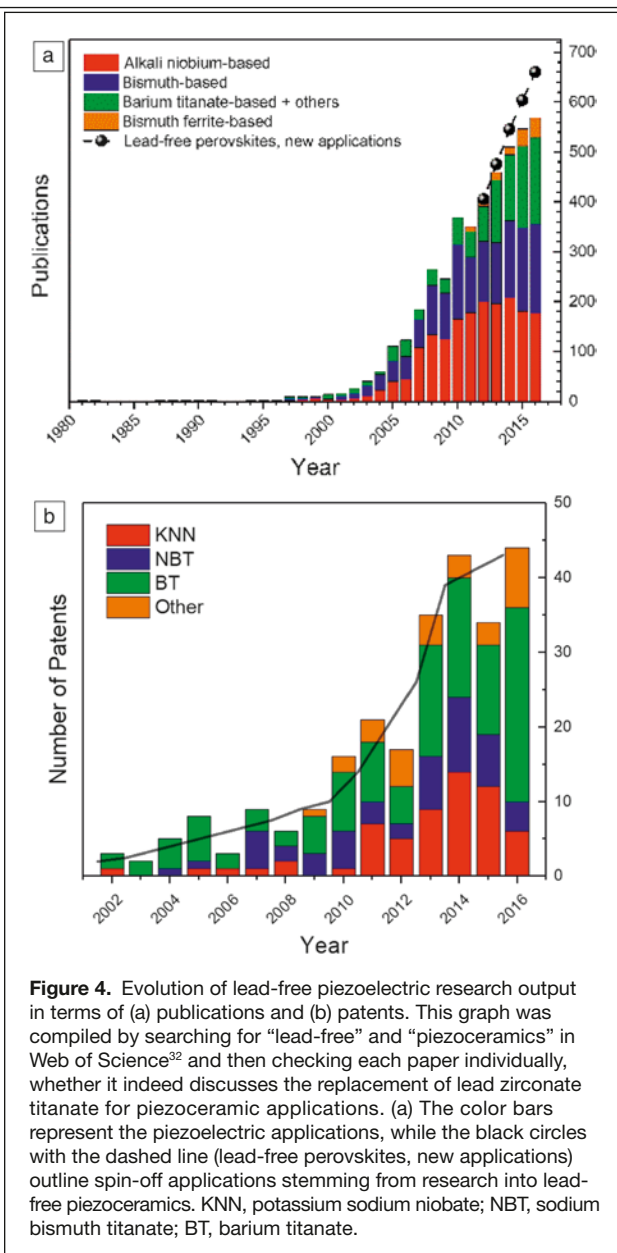



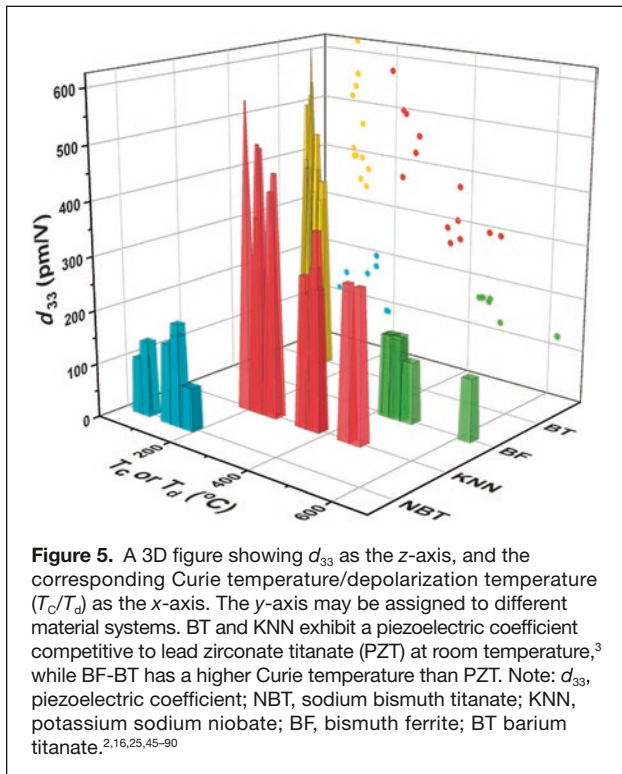

**Figure 5.** A 3D figure showing  $d_{33}$  as the z-axis, and the corresponding Curie temperature/depolarization temperature ( $T_c/T_d$ ) as the x-axis. The y-axis may be assigned to different material systems. BT and KNN exhibit a piezoelectric coefficient competitive to lead zirconate titanate (PZT) at room temperature,<sup>3</sup> while BF-BT has a higher Curie temperature than PZT.<sup>3</sup> Note:  $d_{33}$ , piezoelectric coefficient; NBT, sodium bismuth titanate; KNN, potassium sodium niobate; BF, bismuth ferrite; BT barium titanate.<sup>2,16,25,45-90</sup>

piezoelectric properties) has reached a level sufficient for use in applications (Figure 5<sup>45-90</sup>). In Figure 5, we see that BT and KNN exhibit a piezoelectric coefficient competitive to PZT at room temperature,<sup>3</sup> while BF-BT has a higher Curie temperature than PZT.<sup>3</sup> NBT-BT has advantages with high power applications and mechanical reliability (not covered with this graph). However, at this point in time, we also need to dedicate research efforts into better understanding secondary properties, such as electrical and mechanical properties, electrical fatigue, and machinability.<sup>91</sup> Based on the current level of product development, the article by Shibata et al. in this issue discusses the status of product transfer into applications.<sup>92</sup> At the same time, new materials (e.g., based on bismuth ferrite)<sup>29</sup> and new physical mechanisms are being discovered. In terms of new mechanisms, the opportunities to enhance depolarization temperature by either quenching<sup>93</sup> or using composites<sup>94,95</sup> and by hardening through hard second phases<sup>96</sup> seem particularly noteworthy.

## Acknowledgments

We thank J. Koruza for valuable discussions, and Y. Zhang and F. Weyland for their assistance in figure preparation. J.F.L. thanks the NSFC for support under Grant Nos. 51332002 and 51761135118.

## References

1. EU-Directive 2002/95/EC: "Restriction of the Use of Certain Hazardous Substances in Electrical and Electronic Equipment (RoHS)," *Official Journal of the European Union* **46** (L37), 19 (2003).
2. Y. Saito, H. Takao, T. Tani, T. Nonoyama, K. Takatori, T. Homma, T. Nagaya, M. Nakamura, *Nature* **432**, 84 (2004).
3. T.R. Shrout, S.J. Zhang, *J. Electroceram.* **19**, 113 (2007).

4. B. Jaffe, W.R. Cook, H. Jaffe, *Piezoelectric Ceramics* (Academic Press, Marietta, OH, 1971).
5. S. Trolier-McKinstry, C.A. Randall, *J. Am. Ceram. Soc.* **100**, 3346 (2017).
6. A.J. Bell, O. Deubzer, *MRS Bull.* **43** (8), 581 (2018).
7. J. Rödel, W. Jo, K.T.P. Seifert, E.M. Anton, T. Granzow, D. Damjanovic, *J. Am. Ceram. Soc.* **92**, 1153 (2009).
8. W. Heywang, K. Lubitz, W. Wersing, *Piezoelectricity*, Springer Series in Materials Science (Springer, Berlin, Germany, 2008).
9. R.E. Newnham, *Properties of Materials: Anisotropy, Symmetry, Structure* (Oxford University Press, Oxford, UK, 2005).
10. A.K. Tagantsev, L.E. Cross, J. Fousek, *Domains in Ferroic Crystals and Thin Films* (Springer, New York, 2010).
11. D. Damjanovic, *J. Am. Ceram. Soc.* **88**, 2662 (2005).
12. G.A. Rossetti, A.G. Khachatryan, G. Akcay, Y. Ni, *J. Appl. Phys.* **103**, 114113 (2008).
13. D. Damjanovic, G.A. Rossetti Jr., *MRS Bull.* **43** (8), 588 (2018).
14. K. Uchino, *Ferroelectric Devices* (Marcel Dekker, New York, 2000).
15. T. Ibn-Mohammed, S.C.L. Koh, I.M. Reaney, A. Acquaye, D. Wang, S. Taylor, A. Genovese, *Energy Environ. Sci.* **9**, 3495 (2016).
16. T. Takenaka, K. Maruyama, K. Sakata, *Jpn. J. Appl. Phys. Pt. 1* **30**, 2236 (1991).
17. C. Ma, H. Guo, S.P. Beckman, X. Tan, *Phys. Rev. Lett.* **109**, 107602 (2012).
18. J.E. Daniels, W. Jo, J. Rödel, J.L. Jones, *Appl. Phys. Lett.* **95**, 032904 (2009).
19. A.R. Paterson, H. Nagata, X. Tan, J.E. Daniels, M. Hinterstein, R. Ranjan, P.B. Groszewicz, W. Jo, J.L. Jones, *MRS Bull.* **43** (8), 600 (2018).
20. L.E. Cross, *Nature* **432**, 24 (2004).
21. E. Hollenstein, D. Damjanovic, N. Setter, *J. Eur. Ceram. Soc.* **27**, 4093 (2007).
22. S.J. Zhang, R. Xia, T.R. Shrout, *Appl. Phys. Lett.* **91**, 132913 (2007).
23. R. Wang, H. Bando, T. Katsumata, Y. Inaguma, H. Taniguchi, M. Itoh, *Phys. Status Solidi Rapid Res. Lett.* **3**, 142 (2009).
24. K. Wang, B. Malič, J. Wu, *MRS Bull.* **43** (8), 607 (2018).
25. W.F. Liu, X.B. Ren, *Phys. Rev. Lett.* **103**, 257602 (2009).
26. D.S. Keeble, F. Benabdallah, P.A. Thomas, M. Maglione, J. Kreisel, *Appl. Phys. Lett.* **102**, 092903 (2013).
27. J. Gao, X. Ke, M. Acosta, J. Glaum, X. Ren, *MRS Bull.* **43** (8), 595 (2018).
28. S.O. Leontsev, R.E. Eitel, *J. Mater. Res.* **26**, 9 (2011).
29. M.H. Lee, D.J. Kim, J.S. Park, S.W. Kim, T.K. Song, M.H. Kim, W.J. Kim, D. Do, I.K. Jeong, *Adv. Mater.* **27**, 6976 (2015).
30. S. Kim, G.P. Khanal, H.-W. Nam, J. Fujii, S. Ueno, C. Moriyoshi, Y. Kuroiwa, S. Wada, *J. Appl. Phys.* **122**, 164105 (2017).
31. I. Calisir, D.A. Hall, *J. Mater. Chem. C* **6**, 134 (2018).
32. <https://clarivate.com/products/web-of-science>.
33. M. Li, M.J. Pietrowski, R.A. De Souza, H. Zhang, I.M. Reaney, S.N. Cook, J.A. Kilner, D.C. Sinclair, *Nat. Mater.* **13**, 31 (2014).
34. R. Dittmer, W. Jo, D. Damjanovic, J. Rödel, *J. Appl. Phys.* **109**, 034107 (2011).
35. F. Gao, X. Dong, C. Mao, W. Liu, H. Zhang, L. Yang, F. Cao, G. Wang, *J. Am. Ceram. Soc.* **94**, 4382 (2011).
36. H. Guo, H. Shimizu, Y. Mizuno, C.A. Randall, *J. Appl. Phys.* **117**, 214103 (2015).
37. J. Koruza, B. Rožič, G. Cordoyannis, B. Malič, Z. Kutnjak, *Appl. Phys. Lett.* **106**, 202905 (2015).
38. I. Levin, I.M. Reaney, *Adv. Funct. Mater.* **22**, 3445 (2012).
39. J. Rödel, K.G. Webber, R. Dittmer, W. Jo, M. Kimura, D. Damjanovic, *J. Eur. Ceram. Soc.* **35**, 1659 (2015).
40. Y. Doshida, H. Shimizu, Y. Mizuno, H. Tamura, *Jpn. J. Appl. Phys.* **52**, 07HE01 (2013).
41. S. Kawada, M. Kimura, Y. Higuchi, H. Takagi, *Appl. Phys. Express* **2**, 114401 (2009).
42. K. Shibata, K. Suenaga, A. Nomoto, T. Mishima, *Jpn. J. Appl. Phys.* **48**, 121408 (2009).
43. Z.-Y. Shen, J.-F. Li, R.M. Chen, Q. Zhou, K.K. Shung, *J. Am. Ceram. Soc.* **94** (5), 1346 (2011).
44. J.-F. Li, K. Wang, F.-Y. Zhu, L.-Q. Cheng, F.-Z. Yao, *J. Am. Ceram. Soc.* **96** (12), 3677 (2013).
45. B. Wu, H. Wu, J. Wu, D. Xiao, J. Zhu, S.J. Pennycook, *J. Am. Chem. Soc.* **138**, 15459 (2016).
46. C. Peng, J.-F. Li, W. Gong, *Mater Lett.* **59**, 1576 (2005).
47. Q. Zheng, L. Luo, K.H. Lam, N. Jiang, Y. Guo, D. Lin, *J. Appl. Phys.* **116** (18), 184101 (2014).
48. Q. Zhou, C. Zhou, H. Yang, G. Chen, W. Li, H. Wang, *J. Am. Ceram. Soc.* **95** (12), 3889 (2012).
49. S.O. Leontsev, R.E. Eitel, *J. Am. Ceram. Soc.* **92**, 2957 (2009).
50. T. Zheng, H. Wu, Y. Yuan, X. Lv, Q. Li, T. Men, C. Zhao, D. Xiao, J. Wu, K. Wang, J.-F. Li, Y. Gu, J. Zhu, S.J. Pennycook, *Energy Environ. Sci.* **10**, 528 (2017).

51. W. Jo, J.E. Daniels, J.L. Jones, X. Tan, P.A. Thomas, D. Damjanovic, J. Rödel, *J. Appl. Phys.* **109**, 014110 (2011).
52. W. Li, Z. Xu, R. Chu, P. Fu, G. Zang, *Mat. Sci. Eng. B* **176**, 65 (2011).
53. W. Li, Z. Xu, R. Chu, P. Fu, P. An, *Ceram. Int.* **38**, 4353 (2012).
54. W. Li, Z. Xu, R. Chu, P. Fu, G. Zang, *J. Am. Ceram. Soc.* **94**, 4131 (2011).
55. X. Wang, J. Wu, D. Xiao, J. Zhu, X. Cheng, T. Zheng, B. Zhang, X. Lou, X. Wang, *J. Am. Chem. Soc.* **136**, 2905 (2014).
56. X.X. Wang, X.G. Tang, H.L.W. Chan, *Appl. Phys. Lett.* **85**, 91 (2004).
57. Y. Huang, L. Gao, Y. Hu, H. Du, *J. Mater. Sci. Mater. Electron.* **18**, 605 (2007).
58. Y.-J. Dai, S.-S. He, X. Lao, S.-Z. Zhang, *J. Am. Ceram. Soc.* **97**, 1283 (2014).
59. Y. Chang, Z.-P. Yang, D. Ma, Z. Liu, Z. Wang, *J. Appl. Phys.* **104**, 024109 (2008).
60. L. Gao, Y. Huang, L. Liu, T. Liu, C. Liu, F. Zhou, X. Wan, *J. Mater. Sci.* **43**, 6267 (2008).
61. A. Hussain, C.W. Ahn, J.S. Lee, A. Ullah, I.W. Kim, *Sens. Actuators A Phys.* **158**, 84, (2010).
62. C. Ye, J. Hao, B. Shen, J. Zhai, *J. Am. Ceram. Soc.* **95**, 3577 (2012).
63. C. Zhou, A. Feteira, X. Shan, H. Yang, Q. Zhou, J. Cheng, W. Li, H. Wang, *Appl. Phys. Lett.* **101**, 032901 (2012).
64. D. Maurya, Y. Zhou, Y. Wang, Y. Yan, J. Li, D. Viehland, S. Priya, *Sci. Rep.* **5**, 8595 (2015).
65. D.-S. Yin, Z.-H. Zhao, Y.-J. Dai, Z. Zhao, X.-W. Zhang, S.-H. Wang, *J. Am. Ceram. Soc.* **99**, 2354 (2016).
66. F. Wang, M. Xu, Y. Tang, T. Wang, W. Shi, C.M. Leung, *J. Am. Ceram. Soc.* **95**, 1955 (2012).
67. J. Wu, T. Peng, Y. Wang, D. Xiao, J. Zhu, Y. Jin, J. Zhu, P. Yu, L. Wu, Y. Jiang, *J. Am. Ceram. Soc.* **91**, 319 (2008).
68. J. Wu, Y. Wang, D. Xiao, J. Zhu, P. Yu, L. Wu, W. Wu, *Jpn. J. Appl. Phys.* **46**, 7375 (2007).
69. K. Wang, J.F. Li, N. Liu, *Appl. Phys. Lett.* **93** (9), 092904 (2008).
70. K. Xu, J. Li, X. Lv, J. Wu, X. Zhang, D. Xiao, J. Zhu, *Adv. Mater.* **28**, 8519 (2016).
71. L. Zhu, B. Zhang, L. Zhao, J. Li, *J. Mater. Chem. C* **2**, 4764 (2014).
72. M. Naderer, T. Kainz, D. Schütz, K. Reichmann, *J. Eur. Ceram. Soc.* **34**, 663 (2014).
73. P.-Y. Chen, C.-S. Chen, C.-S. Tu, T.-L. Chang, *J. Eur. Ceram. Soc.* **34**, 4223 (2014).
74. Q. Liu, F.-Y. Zhu, L. Zhao, K. Wang, L. Li, J.-F. Li, W. Jo, *J. Am. Ceram. Soc.* **99**, 3670 (2016).
75. W. Bai, L. Li, W. Li, B. Shen, J. Zhai, H. Chen, *J. Alloys Compd.* **603**, 149 (2014).
76. W. Jo, R. Dittmer, M. Acosta, J. Zang, C. Groh, E. Sapper, K. Wang, J. Rödel, *J. Electroceram.* **29**, 71 (2012).
77. W. Jo, J.-B. Ollagnier, J.-L. Park, E.-M. Anton, O.J. Kwon, C. Park, H.-H. Seo, J.-S. Lee, E. Erdem, R.-A. Eichel, J. Rödel, *J. Eur. Ceram. Soc.* **31**, 2107 (2011).
78. W. Krauss, D. Schütz, F. Mautner, *J. Eur. Ceram. Soc.* **30**, 1827 (2010).
79. W. Li, X. Liu, J. Ma, Y. Wu, Y. Cui, *J. Mater. Sci. Mater. Electron.* **24**, 1551 (2012).
80. W. Li, Z. Xu, R. Chu, P. Fu, G. Zang, M. Narayanan, *J. Am. Ceram. Soc.* **94**, 3181 (2011).
81. X. Li, J. Zhu, M. Wang, Y. Luo, W. Shi, L. Li, J. Zhu, D.J. Xiao, *J. Alloys Compd.* **499**, L1 (2010).
82. X. Zhou, C. Zhou, Q. Zhou, H. Yang, Z. Cen, J. Cheng, L. Cao, Q. Fan, *J. Electron. Mater.* **43** (3), 755 (2014).
83. Y. Hiruma, Y. Imai, Y. Watanabe, H. Nagata, T. Takenaka, *Appl. Phys. Lett.* **92**, 262904 (2008).
84. Y. Hiruma, H. Nagata, T. Takenaka, *J. Appl. Phys.* **105**, 084112 (2009).
85. Y. Sung, J. Kim, J.H. Cho, T.K. Song, M.H. Kim, T.G. Park, *Appl. Phys. Lett.* **98**, 012902 (2011).
86. Y. Zhang, J. Glaum, C. Groh, M.C. Ehmke, J.E. Blendell, K.J. Bowman, M.J. Hoffman, *J. Am. Ceram. Soc.* **97** (9), 2885 (2014).
87. Y.-R. Zhang, J.-F. Li, B.-P. Zhang, C.-E. Peng, *J. Appl. Phys.* **103**, 074109 (2008).
88. Z. Cen, C. Zhou, J. Cheng, X. Zhou, W. Li, C. Yan, S. Feng, Y. Liu, D. Lao, *J. Alloys Compd.* **567**, 110 (2013).
89. Z. Cen, C. Zhou, H. Yang, Qin Zhou, W. Li, C. Yan, L. Cao, J. Song, L. Peng, *J. Am. Ceram. Soc.* **96** (7), 2252 (2013).
90. Z. Yang, B. Liu, L. Wei, Y. Hou, *Mater. Res. Bull.* **43**, 81 (2008).
91. J. Koruza, A.J. Bell, T. Frömling, K.G. Webber, K. Wang, J. Rödel, *J. Materiomics* **4**, 13 (2018).
92. K. Shibata, R. Wang, T. Tou, J. Koruza, *MRS Bull.* **43** (8), 612 (2018).
93. T. Mira, H. Nagata, T. Takenaka, *Jpn. J. Appl. Phys.* **56**, 10PD05 (2017).
94. J. Zhang, Z. Pan, F.-F. Guo, W.-C. Liu, H. Ning, Y.B. Chen, M.-H. Lu, B. Yang, J. Chen, S.-T. Zhang, X. Xing, J. Rödel, W. Cao, Y.-F. Chen, *Nat. Commun.* **6**, 6615 (2015).
95. L.M. Riemer, L.K. Venkataraman, X. Jiang, N. Liu, C. Dietz, R. Stark, P.B. Groszewicz, G. Buntkowsky, J. Chen, S.-T. Zhang, J. Rödel, J. Koruza, *Acta Mater.* **136**, 271 (2017).
96. K.V. Lalitha, L.M. Riemer, J. Koruza, J. Rödel, *Appl. Phys. Lett.* **111**, 022905 (2017). □



**Jürgen Rödel** is a professor in materials science at TU Darmstadt, Germany, distinguished visiting professor at Tsinghua University, China, and specially appointed professor at Tokyo Institute of Technology, Japan. He received his MS degree in materials science from Universität Erlangen-Nürnberg, Germany, and his PhD degree from the University of California, Berkeley. His current interests include the development of lead-free piezoceramics and the concept of mechanically tuned conductivity. He has (co-)authored 300 publications. Rödel received the Deutsche Forschungsgemeinschaft Research Award for both young scientists (Heinz Maier-Leibnitz Prize) and for senior scientists (Gottfried Wilhelm Leibniz Prize). He is a member of the German National Academy of Science and Engineering. Rödel can be reached by email at roedel@ceramics.tu-darmstadt.de.



**Jing-Feng Li** is the Cheung Kong Scholar Distinguished Professor at Tsinghua University, China. He received his PhD degree from Tohoku University, Japan, in 1991, and was an assistant professor and associate professor until joining Tsinghua University as a full professor in 2002. His research interests include piezoelectric and thermoelectric materials and microelectromechanical systems technologies. He has published two books and 400 papers, holds 33 patents, and received the Young Researcher Award from The Japan Institute of Metals and an outstanding young scientist grant from the National Natural Science Foundation of China (NSFC). He is editor-in-chief of the *Journal of Materiomics*. Li can be reached by email at jingfeng@tsinghua.edu.cn.

# GET CONNECTED!

Opt in at [mrs.org/mymrs](https://mrs.org/mymrs)

Set your Materials Research Society alert preferences and be the first to receive ...

- ✓ calls for papers
- ✓ journal alerts
- ✓ and more!